

RILSAN® BUM 30 O

PA11, MR, 18-020, GB30

Rilsan® BUM 30 O resin is a glass bead reinforced polyamide 11 produced from a renewable source. The incorporation of glass beads yields a virtually isotropic reinforced product.

This natural grade dedicated to injection is specially designed for drinking water application: WRAS (UK).

PROPERTIES	DRY / COND	UNIT	TEST STANDARD
RHEOLOGICAL PROPERTIES			
Melt Volume-Flow Rate	20 / *	cm ³ /10 min	ISO 1133
Temperature	235 / *	°C	-
	455 / *	°F	-
Load	5 / *	kg	-
	11 / *	lb	-
Molding Shrinkage, parallel	1.6 / *	%	ISO 294-4, 2577
Molding Shrinkage, normal	1.4 / *	%	ISO 294-4, 2577
MECHANICAL PROPERTIES			
Tensile Modulus	- / 1850	MPa	ISO 527-1/-2
	- / 268000	psi	
Stress at Break	- / 31	MPa	ISO 527-1/-2
	- / 4500	psi	
Strain at Break	- / 40	%	ISO 527-1/-2
Shore D Hardness, after 15 s	71 / *	-	ISO 868
Charpy Impact Strength, +23°C	- / 96	kJ/m ²	ISO 179/1eU
	- / 45.7	ftlb/in ²	
Charpy Impact Strength, -30°C	- / 96	kJ/m ²	ISO 179/1eU
	- / 45.7	ftlb/in ²	
Charpy Notched Impact Strength, +23°C	- / 6	kJ/m ²	ISO 179/1eA
	- / 2.85	ftlb/in ²	
Charpy Notched Impact Strength, -30°C	- / 5	kJ/m ²	ISO 179/1eA
	- / 2.38	ftlb/in ²	
THERMAL PROPERTIES			
Melting Temperature, 10°C/min	189 / *	°C	ISO 11357-1/-3
Temp. of Deflection Under Load, 1.80 MPa	60 / *	°C	ISO 75-1/-2
	140 / *	°F	
Temp. of Deflection Under Load, 0.45 MPa	165 / *	°C	ISO 75-1/-2
	329 / *	°F	

Arkema France - A French "société anonyme", registered in the Nanterre (France) Trade and Companies Register under the number 319 632 790 SDC/11-2018
 Source: automatically generated TDS from Material Database on 12-08-2024

RILSAN® BUM 30 O

Vicat Softening Temperature, 50°C/h 50N	165 / *	°C	ISO 306
	329 / *	°F	
Coeff. of Linear Thermal Expansion, parallel	70 / *	E-6/K	ISO 11359-1/-2
Burning Behav. at 1.5 mm Nominal Thickness	HB / *	class	IEC 60695-11-10
Thickness Tested	1.6 / *	mm	-
	0.0630 / *	in	
Burning Behav. at Thickness h	HB / *	class	IEC 60695-11-10
Thickness Tested	3.2 / *	mm	-
	0.1260 / *	in	
ELECTRICAL PROPERTIES			
Volume Resistivity	- / 1E12	Ohm* m	IEC 62631-3-1
Surface Resistivity	* / 1E14	Ohm	IEC 62631-3-2
Dielectric (Electric) Strength	- / 40	kV/mm	IEC 60243-1
	- / 1020	kV/in	
Comparative Tracking Index	* / 600	-	IEC 60112
OTHER PROPERTIES			
Water Absorption, 23°C, immersion, equilibrium	1.3 / *	%	ISO 62
Density	1230 / 1230	kg/m ³	ISO 1183
	1.23 / 1.23	g/cm ³	

MAIN APPLICATIONS:

- Drinking water applications

PACKAGING:


This grade is delivered dried in sealed packaging (25 kg bags) ready to be processed.

SHELF LIFE:


Two years from the delivery. For any use above this limit, please refer to our technical services.

DIAGRAMS


VISCOSITY-SHEAR RATE

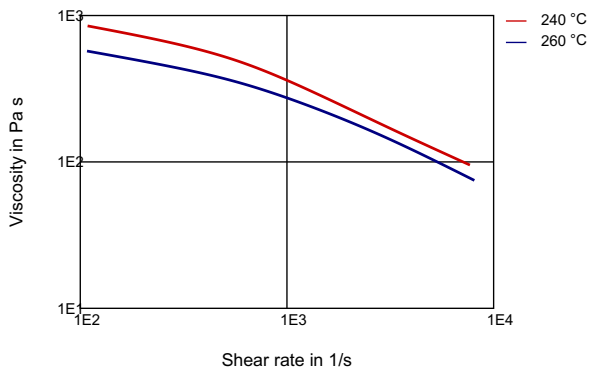

SHEARSTRESS-SHEAR RATE

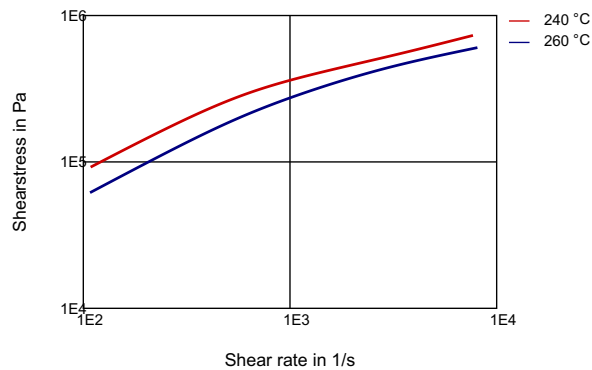

DYN. SHEAR MODULUS-TEMPERATURE

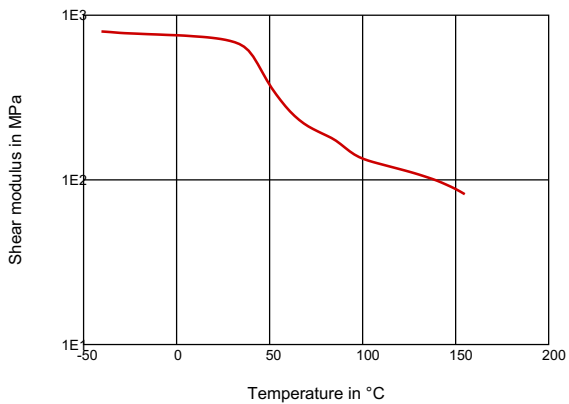

Processing conditions:

- Typical melt temperature (Min / Recommended / Max) : 250°C / 270°C / 290°C.
- Mold temperature : 40 - 90°C
- Drying time and temperature (only necessary for bags opened for more than two hours) : 4-6 hours at 80-90°C.

RILSAN[®] BUM 30 O

<p>PROCESSING</p> <p>Injection Molding</p>	<p>Headquarters:</p> <p>Arkema France 420 rue d'Estienne d'Orves 92705 Colombes Cedex France T +33 (0)1 49 00 80 80 hpp.arkema.com</p> <p>Arkema Inc. – High Performance Polymers</p> <p>900 First Avenue King of Prussia, PA 19406 Tel.: +1 610 205 7000 hpp.arkema.com</p>
<p>DELIVERY FORM</p> <p>Pellets</p>	
<p>ADDITIVES</p> <p>Release agent</p>	
<p>SPECIAL CHARACTERISTICS</p> <p>Bio-Based</p>	
<p>REGIONAL AVAILABILITY</p> <p>North America, Europe, Asia Pacific, South and Central America, Near East/Africa</p>	

The statements, technical information and recommendations contained herein are believed to be accurate as of the date hereof. Since the conditions and methods of use of the product and of the information referred to herein are beyond our control, ARKEMA expressly disclaims any and all liability as to any results obtained or arising from any use of the product or reliance on such information; NO WARRANTY OF FITNESS FOR ANY PARTICULAR PURPOSE, WARRANTY OF MERCHANTABILITY OR ANY OTHER WARRANTY, EXPRESSED OR IMPLIED, IS MADE CONCERNING THE GOODS DESCRIBED OR THE INFORMATION PROVIDED HEREIN. The information provided herein relates only to the specific product designated and may not be applicable when such product is used in combination with other materials or in any process. The user should thoroughly test any application before commercialization. Nothing contained herein constitutes a license to practice under any patent and it should not be construed as an inducement to infringe any patent and the user is advised to take appropriate steps to be sure that any proposed use of the product will not result in patent infringement.

Arkema France - A French "société anonyme", registered in the Nanterre (France)
 Trade and Companies Register under the number 319 632 790 SDC/11-2018
 Source: automatically generated TDS from Material Database on 12-08-2024